



DuPont™ Kapton® HPP-ST

Polyimide Film

Description

DuPont™ Kapton® HPP-ST is a two-sided, treated film that offers the same excellent balance of physical, chemical, and electrical properties over a wide temperature range offered by general purpose Kapton® HN. Additionally, this high performance film has superior dimensional stability and excellent adhesion with most adhesion systems. Adhesion data for HPP-ST can be referenced in the adhesion to Kapton® technical bulletin.

In applications where low shrinkage and superior adhesion are important, Kapton® HPP-ST is the polyimide film of choice.

Applications

- Electronic parts
- PCB stencils
- Screen printing
- Insulation tubing

Product Specifications

Kapton® HPP-ST is manufactured, slit and packaged according to the product specifications listed in H-38479 (6/18).

Certification

Kapton® HPP-ST meets ASTM D-5213 (type 1, item A) requirements.

Table 1 – Typical Properties of Kapton® HPP-ST at 23°C (73°F)

Property	Unit	1 mil 25µm	2 mil 50µm	3 mil 75µm	5 mil 125µm	Test Method
Physical						
Tensile Strength	kpsi (MPa)	33.5 (231)	34 (234)	34 (234)	33.5 (231)	ASTM D-882-91
Elongation	%	72	72	78	82	ASTM D-882-91
Tensile Modulus	kpsi (GPa)	400 (2.8)	400 (2.8)	400 (2.8)	400 (2.8)	ASTM D-882-91
Adhesion	pli (N/mm)	10 (1.8)	10 (1.8)	10 (1.8)	10 (1.8)	IPC-TM-650 Method 2.4.9*
Density	g/cc	1.42	1.42	1.42	1.42	ASTM D-1505-90
MIT Folding Endurance	cycles	285,000	55,000	6,000	3,000	ASTM D-2176-89
Tear Strength-propagating (Elmendorf), N		0.07	0.21	0.38	0.58	ASTM D-1922-89
Tear Strength, initial (Graves), N		7.2	16.3	26.3	46.9	ASTM D-1004-90
Thermal						
Flammability		94V0	94V0	94V0	94V0	UL-94
Shrinkage (30 min at 150°C) Method 2.2.4A	%	0.03	0.03	0.03	0.03	IPC-TM-650
Limiting Oxygen Index	%	37	43	46	45	ASTM D-2863-87
Electrical						
Dielectric Strength	kV/mil (kV/mm)	7.7 (303)	6.1 (240)	5.1 (201)	3.9 (154)	ASTM D-149-91
Dielectric Constant	1kHz	3.4	3.4	3.5	3.5	ASTM D-150-92
Dissipation Factor at 1 kHz		0.0018	0.0020	0.0020	0.0026	ASTM D-150-92
Volume Resistivity	ohm-cm	1.5 x 10 ¹⁷	1.5 x 10 ¹⁷	1.4 x 10 ¹⁷	1.0 x 10 ¹⁷	ASTM D-257-91

Acrylic adhesive to 1 oz. copper

Table 2 – Physical Properties of Kapton® HPP-ST Film

Property	Typical Value at		Test Method
	23°C (73°F)	200°C (392°F)	
Yield Point at 3%, MPa (psi)	69 (10,000)	41 (6000)	ASTM D-882-91
Stress to produce 5% elongation, MPa (psi)	90 (13,000)	62 (9000)	ASTM D-882-91
Impact Strength, N·cm· (ft lb)	78 (0.58)		DuPont Pneumatic Impact Test
Coefficient of Friction, kinetic (film-to-film)	0.48		ASTM D-1894-90
Coefficient of Friction, static (film-to-film)	0.63		ASTM D-1894-90
Refractive Index (sodium D line)	1.70		ASTM D-542-90
Poisson's Ratio	0.34		Avg. three samples Elongated at 5%, 7%, 10%
Low Temperature Flex Life	pass		IPC-TM 650, Method 2.6.18

Table 3 – Thermal Properties of DuPont™ Kapton® HPP-ST Film

Thermal Property	Typical Value	Test Condition	Test Method
Melting Point	None	None	ASTM E-794-85 (1989)
Thermal Coefficient of Linear Expansion	20 ppm/°C (11 ppm/°F)	-14 to 38°C (7 to 100°F)	ASTM D-696-91
Coefficient of Thermal Conductivity, W/m·K (cal/sec-cm·°C)	0.20 (4.8 x 10 ⁻⁴)	296 K (23°C)	ASTM D5470
Specific Heat, J/g·K (cal/g·°C)	1.09 (0.261)		Differential calorimetry
Heat Sealability	not heat sealable		
Solder Float	pass		IPC-TM-650, method 2.4.13A
Smoke Generation	D _m =<1	NBS smoke chamber	NFPA-258
Glass Transition Temperature (Tg)	A second order transition occurs in Kapton® between 360°C(680°F) and 410°C(770°F) and is assumed to be the glass transition temperature. Different measurement techniques produce different results within the above temperature range.		

Table 4 – Electrical Properties of Kapton® HPP-ST Film at 23°C (73°F)

Property Film Gage	Typical Value		Test Condition	Test Method
Dielectric Strength	V/m kV/mm	(V/mil)	60 Hz 1/4 in electrodes 500 V/sec rise	ASTM D-149-91
	25 µm (1 mil)	303 (7700)		
	50 µm (2 mil)	240 (6100)		
	75 µm (3 mil)	201 (5100)		
125 µm (5 mil)	154 (3900)			
Dielectric Constant			1 kHz	ASTM D-150-92
	25 µm (1 mil)	3.4		
	50 µm (2 mil)	3.4		
	75 µm (3 mil)	3.5		
125 µm (5 mil)	3.5			
Dissipation Factor			1 kHz	ASTM D-150-92
	25 µm (1 mil)	0.0018		
	50 µm (2 mil)	0.0020		
	75 µm (3 mil)	0.0020		
125 µm (5 mil)	0.0026			
Volume Resistivity	Ω·cm ¹⁷			ASTM D-257-91
	25 µm (1 mil)	1.5 x 10 ¹⁷		
	50 µm (2 mil)	1.5 x 10 ¹⁷		
	75 µm (3 mil)	1.4 x 10 ¹⁷		
	125 µm (5 mil)	1.0 x 10 ¹⁷		

Dimensional Stability

The dimensional stability of DuPont™ Kapton® polyimide film depends on two factors—the normal coefficient of thermal expansion and the residual stresses placed in the film during manufacture. The latter causes Kapton® to shrink on its first exposure to elevated temperatures as indicated in the bar graph in **Figure 1**. Once the film has been exposed, the normal values of the thermal coefficient of linear expansion as shown in **Table 5** can be expected.

Residual Shrinkage vs. Exposure Temperature and Thickness, Kapton® HN and HPP-ST Films

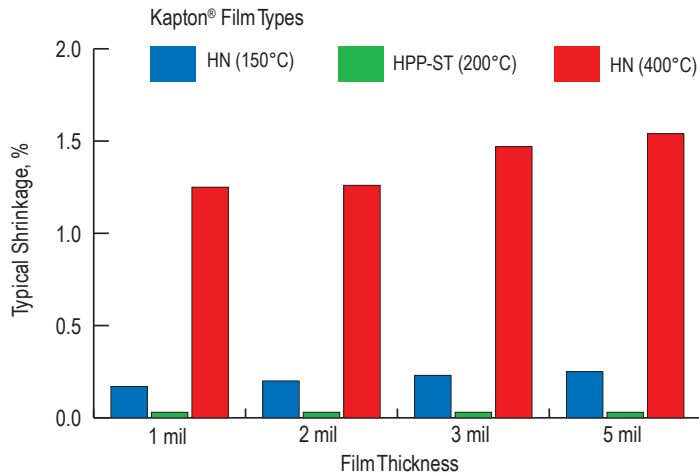


Table 5 – Thermal Coefficient of Expansion, Kapton® HPP-ST Film, 25 µm (1 mil), Thermally Exposed

Temperature Range, °C, (°F)	ppm/°C
30–100 (86–212)	17
100–200 (212–392)	32
200–300 (392–572)	40
300–400 (572–752)	44
30–400 (86–752)	34



For more information on DuPont™ Kapton® or other DuPont products, please visit our website.

kapton.com

The information provided in this data sheet corresponds to our knowledge on the subject at the date of its publication. It may be subject to revision as new knowledge and experience becomes available. This information is not intended to substitute for any testing you may need to conduct to determine for yourself the suitability of our products for your particular purposes. Since we cannot anticipate all variations in end-use and disposal conditions, DuPont makes no warranties and assumes no liability in connection with any use of this information. It is intended for use by persons having technical skill, at their own discretion and risk. Nothing in this publication is to be considered as a license to operate under or a recommendation to infringe any patent right.

CAUTION: Do not use in medical applications involving permanent implantation in the human body. For other medical applications, see "DuPont Medical Applications CAUTION" and "DuPont Medical Applications POLICY" statements. These documents are available upon request.

DuPont™, the DuPont Oval Logo, and all products, unless otherwise noted, denoted with ™, ® or ® are trademarks, service marks or registered trademarks of affiliates of DuPont de Nemours, Inc. Copyright © 2021 DuPont de Nemours Inc. All rights reserved.

EI-10207 (05/21)